

# Miscanthus

REFERENCE MATERIAL

## Pedigree

Institution: AGgrow Tech	Harvested: 2014
Location: Tifton, GA	Received at INL: 2014
Scientific Name: <i>Miscanthus × giganteus</i>	Sample Preparation: 1-inch chopped using a Claas Forage Chopper
Variety: Freedom	

## Composition

**Table 1.** Chemical composition<sup>a</sup> of Reference Miscanthus (mean of analyses completed 2/2015 & 4/2015)

%Structural Ash	%Extractable Inorganics	%Structural Protein	%Extractable Protein	%Water Extracted Glucan <sup>b</sup>
0.52	0.02	0.47	0.16	0.27
%Water Extracted Xylan <sup>b</sup>	%Water Extractives Others	%EtOH Extractives	%Lignin	%Glucan
0.10	2.61	2.05	20.41	40.79
%Xylan	%Galactan	%Arabinan <sup>c</sup>	%Acetate	%Total
22.01	1.11	2.86	3.87	97.25

<sup>a</sup>Determined using NREL “Summative Mass Closure” LAP (NREL/TP-510-48087)

<sup>b</sup>Determined by HPLC following an acid hydrolysis of the water extractives

<sup>c</sup>%Arabinan value includes %mannan, because arabinose and mannose co-elute on the HPLC column

## Proximate, Ultimate & Calorimetry

**Table 2.** Proximate, ultimate, and calorific values for Reference Miscanthus (reported on a dry basis; completed 11/2014)

Proximate <sup>a</sup>			Ultimate <sup>b</sup>					Calorimetry <sup>c</sup>	
%Volatile	%Ash	%Fixed Carbon	%Hydrogen	%Carbon	%Nitrogen	%Oxygen	%Sulfur	HHV	LHV
85.53	1.40	13.06	5.85	50.64	0.21	41.88	0.01	8493	7073

<sup>a</sup>Proximate analysis was done according to ASTM D 5142-09

<sup>b</sup>Ultimate analysis was conducted using a modified ASTM D5373-10 method (Flour and Plant Tissue Method) that uses a slightly different burn profile. Elemental sulfur content was determined using ASTM D4239-10, and oxygen content was determined by difference

<sup>c</sup>Heating values (HHV, LHV) were determined with a calorimeter using ASTM D5865-10

## Elemental Ash

**Table 3.** Elemental ash composition<sup>a</sup> of Reference Miscanthus (completed 4/2015)

%Al as Al <sub>2</sub> O <sub>3</sub>	%Ca as CaO	%Fe as Fe <sub>2</sub> O <sub>3</sub>	%K as K <sub>2</sub> O	%Mg as MgO	%Mn as MnO	%Na as Na <sub>2</sub> O	%P as P <sub>2</sub> O <sub>5</sub>	%Si as SiO <sub>2</sub>	%Ti as TiO <sub>2</sub>	%S as SO <sub>3</sub>
0.29	18.34	1.20	6.44	9.03	1.11	0.18	3.58	52.31	0.02	3.15

<sup>a</sup>Determined as described in ASTM standards D3174, D3682 and D6349


## Lignin Chemistry

**Table 4.** Lignin chemistry of Reference Miscanthus (completed 1/2016)

Monolignol Composition <sup>a</sup>			Cinnamate Content <sup>a</sup>	
p-Hydroxyphenyl (H) content (% of total H+G+S)	Guaiacyl (G) content (% of total H+G+S)	Syringyl (S) content (% of total H+G+S)	Ferulate content (% of total cinnamates)	p-Coumarate (% of total cinnamates)
2	66	32	34	66

<sup>a</sup>Determined by integration of peak volumes of ball-milled whole cell wall samples, swelled in 4:1 DMSO:Py, and analyzed by gel-state HSQC NMR (Mansfield, S. D.; Kim, H.; Lu, F.; Ralph, J. (2012). Nature Protocols, 7(9), 1579-1589)

## Particle Characteristics

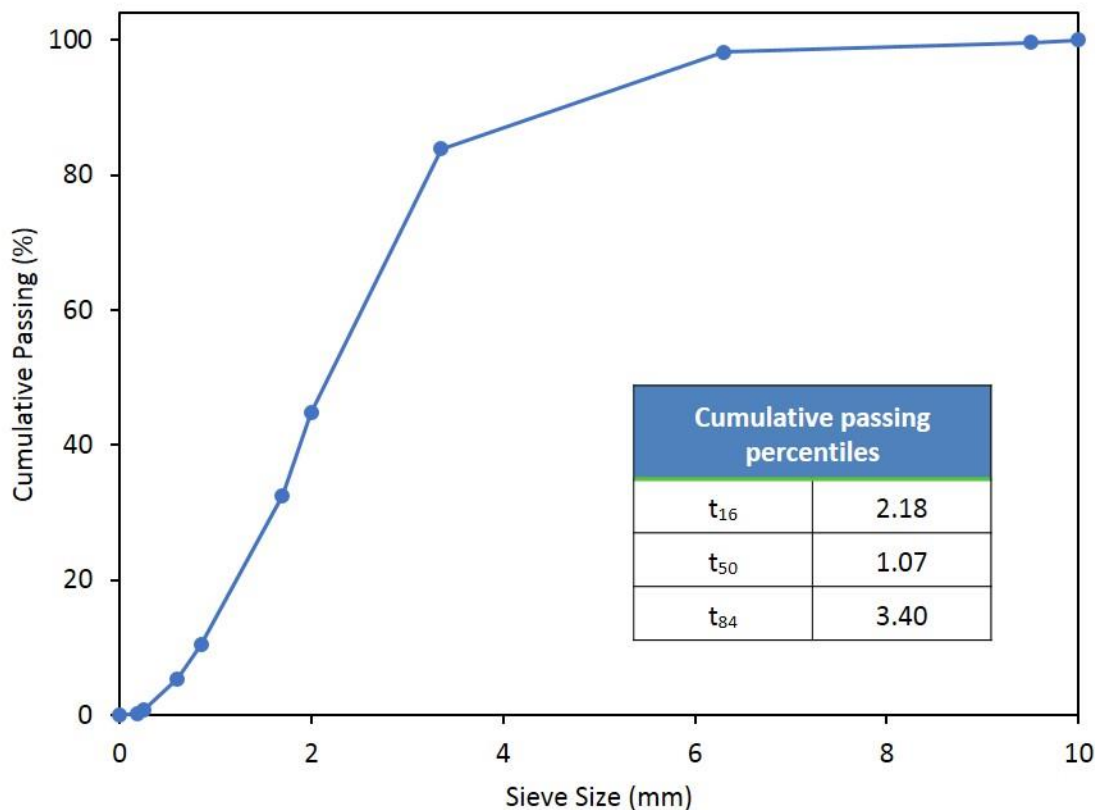

**Figure 1.** Cumulative passing percent of 1-inch Reference Miscanthus determined according to ANSI/ASAE S319.4 using a Ro-Tap test sieve shaker (Model RX-29, W.S. Tyler) and a 15 minute total sieving time (completed 4/2015). The cumulative passing percentile sieve sizes (e.g.,  $t_{16}$ ) were calculated by interpolation and represent theoretical sieve sizes that would retain 16, 50 or 84% of the particles by mass.

## Contact

For questions regarding biomass material or analytical data please contact Amber Hoover at [amber.hoover@inl.gov](mailto:amber.hoover@inl.gov) or 208-526-5992.

Visit the Bioenergy Feedstock Library (<https://bioenergylibrary.inl.gov>) for more information on biomass feedstocks.

Revised on 7/10/2019.